

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 24 SEP 2004		2. REPORT TYPE Technical, Success Stories		3. DATES COVERED 19-05-2004 to 23-09-2004	
4. TITLE AND SUBTITLE CH-53 Gun Yoke				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER 04-0036-04	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Center for Defense Manufacturing & Machining,1600 Technology Way,Latrobe,PA,15650				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT Augustine Die & Mold, Inc, of Somerset, Pa., is producing gun turret components for various military helicopters, including the Sikorsky CH-53. Machining a 12" wide, 18" long, 10" thick, horseshoe-shaped aluminum gun yoke was a challenge; roughing operations alone were taking over 3-4 hours for each yoke. Additionally, existing processes created stresses that distorted the part, requiring straightening operations that consumed about anhour. Augustine sought the help of NCDMM to reduce machining time and eliminate residual stress.					
15. SUBJECT TERMS NCDMM; Augustine Die & Mold, Inc; Sikorsky CH-53					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT 1	18. NUMBER OF PAGES 1	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			


PROBLEM / OBJECTIVE

Augustine Die & Mold, Inc. of Somerset, Pa., is producing gun turret components for various military helicopters, including the Sikorsky CH-53. Machining a 12" wide, 18" long, 10" thick, horseshoe-shaped aluminum gun yoke was a challenge; roughing operations alone were taking over 3-4 hours for each yoke. Additionally, existing processes created stresses that distorted the part, requiring straightening operations that consumed about an hour. Augustine sought the help of NCDMM to reduce machining time and eliminate residual stress.

ACCOMPLISHMENTS / PAYOFF

Process Improvement

NCDMM analyzed the operation and applied modal analysis technologies from alliance partners Design & Manufacturing Solutions, Inc. (DMS) and Manufacturing Laboratories, Inc. (MLI). Modal analysis can determine the cutting characteristics of individual tools while they are mounted in the machine tool. The information is used to create stability lobe diagrams revealing the combinations of cutting speeds and feed rates that can best deliver high productivity without chatter.

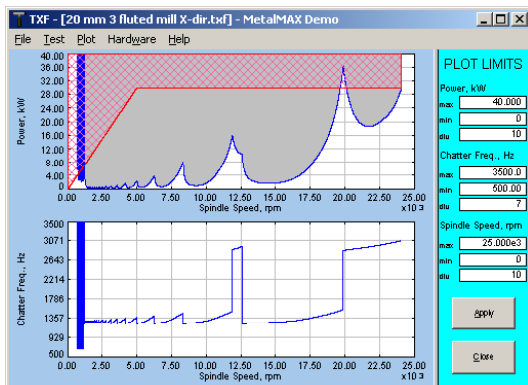


Stability
Lobe
Diagram

NCDMM also recommended the application of the new Mill 1 indexable insert endmills featuring insert coatings designed especially for milling of aluminum by alliance partner Kennametal Inc. The Mill 1 tool and advanced programming techniques aided in the reduction of both machining time and of the number of tools required to machine the part.

Implementation and Technology Transfer

The modal analysis indicated that chatter-free operation could be achieved at an 8,000 revolutions per minute (rpm) spindle speed and 300 inches per minute (ipm) feed rate, compared to the 4,500 rpm and 90 ipm used previously. NCDMM demonstrated a "proof-of-concept" part to confirm the analysis.

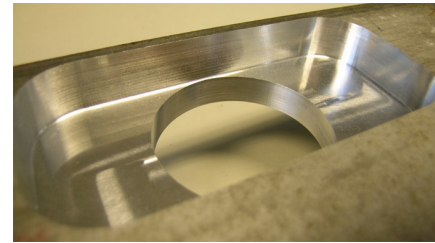

"Proof-of-
Concept" Part

Roughing time dropped from over three hours to approximately 25 minutes. The new cutting parameters and tooling significantly reduced cutting forces. Stress and distortion were eliminated, as was the time required to straighten the workpiece.

Expected Benefits

In summary, implementation produced:

- An immediate 85 percent reduction in time required for roughing
- Elimination of time required for straightening operations
- Reductions in finishing operations

Further savings are expected following full implementation of NCDMM recommendations. Savings of \$40,000 over the length of the initial order will be realized based on the average hourly rate for this area. **NOTE:** Savings based on an average \$60/hour shop rate for the Southwest Pa. area.

TIME LINE / MILESTONE

Start Date May 04
End Date September 04

PROJECT FUNDING

NCDMM funding \$10K

PARTICIPANTS

Augustine Die & Mold, Inc.
Design & Manufacturing Solutions, Inc. (DMS)
Kennametal Inc.
Manufacturing Laboratories, Inc. (MLI)

For additional information concerning this project, contact the NCDMM at www.ncdmm.org